

Enhancement the conductivity and flexibility of fabricated chip comprise from nano graphene metals assembled on polymeric PEI- PDMS matrix

Ameen Abdelrahman^{a*}, Fouad Erchiqui^a and Nedil Mourad^b

^aSchool of Engineering, Université du Québec en Abitibi-Témiscamingue, 445 Boulevard de l'Université Rouyn-Noranda (QC) J9X 5E4, Canada

^bSchool of Engineering, Université du Québec en Abitibi-Témiscamingue, Campus de Val d'Or, 675, 1ère Avenue, Val d'Or, Québec, J9P 1Y3, Canada

ARTICLE INFO

Article history:

Received 26 January 2022

Accepted 10 April 2022

Available online

11 April 2022

Keywords:

Copolymers

Impedance

Assembled metals

Graphene

Self-Healing

Spectroscopic analyses

Mechanical characterization

ABSTRACT

This work aims to make a unique polymer to be used as a conductive and flexible chip antenna. Its properties are robustness, rigidity, stretchability, and good conduction. The fabricated composite is composed of two copolymers, Polydimethylsiloxane (PDMS) and Polyethylenimine (PEI), assembled with nano metals (Copper, Silver), and graphene nanoparticles as a matrix. Nano metals fill out the inter-layer space, and polymer voids reinforce the cross linker. Graphene/metal nanoparticles help make chelating complexes using metallic bonds, enhancing the polymer's conductivity from 1.87×10^{-4} to $5.64 \times 10^{-6} \sigma \text{ Scm}^{-1}$. The conductivity, self-healing, and surface morphology of fabricated composite are analyzed using different spectroscopic techniques, such as electrochemical impedance (EIS), Scanning Electronic Microscopy (SEM), Transition Electronic Microscopy (TEM), Infrared spectroscopy (IR), UV-Visible spectroscopy (UV), and a particle size analyzer.

© 2022 Growing Science Ltd. All rights reserved.

Abbreviation

PDMS	Polydimethylsiloxane
EIS	Electrochemical Impedance Spectroscopy
CV	Cyclic voltammetry
DSC	Differential scanning calorimetry
TEM	Transmission electron microscopy
UV	Ultraviolet-visible spectroscopy
MEMS	Microelectromechanical systems
AC	Alternative-current
OCV	Open cycle volt
SEM	Scanning electron microscopy
NPs-	Nano particles
PEI	Polyethylenimine
ICP	Ion coupled plasma

1. Introduction

Flexible (stretchable) electronics fabricated with electronic innovation technology incorporates an organic/inorganic conductive component with nonconductive polymers or metal deposits substrates. Stretchable electronics have gotten much attention due to their unique properties like efficiency, flexibility/ductility, low-cost cook-up processes, and broader

* Corresponding author.

E-mail addresses: Abda02@uqat.ca (A. Abdelrahman)

application potential in displays, biosensors, RFID, wearable antenna tags, and devices (Noh, 2016). One important value of stretchable electronics is that materials keep conductivity under great strain during mechanical movement. The highly diverse properties of polymeric materials such as healing, flexibility, robustness, and conductivity are the main reasons they are applicable in different fields. They are particularly useful when integrated or impregnated with different materials, like silver nanowire (AgNW) (Woo et al., 2014; Zhang et al., 2018), carbon nanotubes (CNT) (Shin et al., 2010; Cai et al., 2016), graphene (GR) (Kim et al., 2009; Stankovich et al., 2006; Yan et al., 2014; Chen et al., 2014), polyaniline (PANI) (Yakuphanoglu & Şenkal, 2007), or polypyrrole (PPY) (Fu & Manthiram, 2012; Borah et al., 2013).

Poly(dimethylsiloxane) (PDMS) is one of the most likely di-electric materials used to fabricate microfluidic electronic devices. The material's cost, simple fabrication process, rapid prototyping, excellent optical transparency, and gas permeability have been widely publicized. Although PDMS has many advantages, its high hydrophobicity (water contact angle $\sim 108^\circ \pm 7^\circ$) usually limits its applications. Recently, copolymers have been getting more attention due to their applications in aerospace, microelectronics, printed circuits, adhesives, thermoplastic elastomers, and organophilic pervaporation (Arnold et al., 1989; Mahoney et al., 2002; Hamciuc et al., 2009; McGrath et al., 1999). Furthermore, the high demand for microelectronics and nanoelectronic devices increases because they are highly-precious and used to control dimensional structures in wafer-scale manufacturing (Freebody, 2011; Borah et al., 2013; Mack, 2011; Raquez, 2013). The device invention methodologies are already well known in electronic manufacture using silicon chips miniaturization on a large scale (Vaglio Pret, 2012; Biswas, 2012).

On the other hand, alternative methodology builds on approaches to block copolymer (BCP) as self-assembly nanostructure creation is increasingly and rapidly approached by researchers (Darling, 2007). Approaches can create sub-10 nm structures with low costs (Li & Huck, 2004; Kim et al., 2016). BCPs like polyethyleneimine -b- polymethylmethacrylate (PEI-b-PMMA), polylactic acid-b-polystyrene (PLA-b-PS), polystyrene-b-polydimethylsiloxane (PS-b-PDMS), and polyethylene oxide-b-polystyrene (PEO-b-PS) of cylindrical, lamellar, or spherical structure joints in different strategies to modify or control the substrate and alignment pattern have been used to pioneer nano lithographic disassembly (Ghoshal et al., 2012; Hirai et al., 2009). However, conventional conductors are not stretchable, while traditional elastomers like polystyrene, natural rubber (NR), and poly(dimethylsiloxane) (PDMS) are not conductive. Two methods have been used to achieve stretchable interconnected interlink filler. The first involves making wavy or mesh configurations by adding conductive materials, materials with tensile strain, and elastic materials (Lee et al., 2012). The second method involves filling the gaps or interspace of polymers with conducting material (Xu & Zhu, 2012; Gaynor, 2011).

Copolymerization is one of the best ways to prepare new polymeric materials. By combining two structures, its specific properties have different chemical or physical properties as one block polymer chain. It has been established that the integration between polysiloxane and polyimide improves efficiency and polyimide's processability and its mechanics augment polysiloxane's properties. The other beneficial properties of poly(imide siloxane) copolymers should be considered, high hydrophobicity, oxidizing resistance to other oxidizing agents and environment, and adhesion di-electric constants, high flexibility, and robustness (Arnold et al., 1989; Mahoney et al., 2002; Hamciuc et al., 2009; McGrath et al., 1999; Chen et al., 2013; Krea et al., 2004; Wohl et al., 2012). Moreover, the stability (thermoplastics to thermoplastic elastomers) of poly(imide siloxane) copolymers, which based on composition and structure (Yilgör & McGrath, 1988; Liaw et al., 2008). Therefore, the copolymers have become highly sought after for many applications such as microelectronic, adhesives, biosensors, communication, and aerospace applications (Arnold et al., 1989; Chen et al., 2013; Liaw et al., 2008). PDMS is characterized by a low glass transition temperature of -127°C , in addition to the shear elastic modulus 250 kPa, while a specific gravity range between 0.91 to 1.00 with a molecular weight of $10\text{--}60 \times 10^3 \text{ gmol}^{-1}$. PDMS is an inert polymer and hydrophobic chemical environment partially dissolved in solvents such as pentane, xylene, and trimethylamine (Mata et al., 2005). Studies show that carbon nanotubes (CNTs) have an electrical conductivity of $10^4\text{--}10^5 \text{ S cm}^{-1}$, high carrier mobility of $1000\text{--}4000 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$, thermal stability up to 700°C in air Young's models of between 0.27–1.25 TPa, and thermal conductivity of $3000\text{--}6600 \text{ W m}^{-1} \text{ K}^{-1}$ (Baughman et al., 2002; Lee et al., 2011; Jiao et al., 2012). The electrically conductive CNT/polymer composites have potential applications, especially in electromagnetic shielding, (Coleman et al., 2006; Mirkhani et al., 2017) energy harvesting, biomedical devices., supercapacitors, (Hamra et al., 2018; Li et al., 2014) sensors, (Hwang et al., 2011; Pötschke et al., 2011) and smart actuators (Yu et al., 2012; Yadav et al., 2013). Since CNT/polymer composites are mechanically resilient, cost-effective, lightweight, easily process able, scalable, and compliant, they can be used in electric heating elements (McGrath et al., 1999; Freebody et al., 2011; Borah et al., 2013). Polydimethylsiloxane (PDMS), a type of silicon-based elastomer, has excellent properties, including optical transparency, chemical/biological extinction, flexibility, nontoxicity, and gas permeability (Mao et al., 2001; Kim & Yun, 2013). PEI (polyethyleneimine) is applicable in different industries. Its various properties, like water base polymer selectivity (it dissolves in hot water), give it good chemical and thermal stability and mechanical properties (Liu et al., 2002). Different studies have been done on the assembly of a PEI/metal complex. For instance, Kurdi and Tremblayas' work on hollow fiber membranes used O_2/N_2 adsorption on the surfaces (Kurdi & Tremblay, 2003). Ren et al. have also studied the effect of different solvents on PEI's morphology (Ren et al., 2010).

This paper aims to describe the fabrication of a flexible conductor copolymer composed of polyethyleneimine and polydimethylsiloxane assembled in a thin layer of graphene and nanoparticulate metals made from silver and copper. Various characterizations have been conducted on copolymers to evaluate which composite can produce a flexible, stretchable antenna in future work.

2. Materials and Methods

2.1. Materials

Graphene Nano powders (purity > 99%, 300 mesh) were supplied by Sigma-Aldrich Co., Ltd. (Canada). Most of the others chemicals(, CuSO_4 , AlCl_3 and AgNO_3 ,) used for prepared electrolyte salt solution were acquired by scientific fisher Toronto, Canada. Polyethylenimine (PEI), n-Hexane, and THF were purchased from Sigma Aldrich, Canada. Polydimethylsiloxane (PDMS) was purchased from Sylgard R 184, Dow Corning Corporation, and Canada.

2.2 Methods

2.2.1 Assembly of Nano Graphene on PDMS

By taken specific quantities of 3 mg/mL PDMS, 2 ml of Tetrahydrofuran (THF), and (6 mg) of Graphene Nano powder was added to a 100 ml glass beaker and mixed until homogenous using an XHF-DY homogenizer at 3500 rpm for 15 minutes. The colloidal solution was then further mixed using ultrasonication with adjustable t temperature at 45 °C for one hour.

2.2.2 Preparation of the PEI composites matrix

We took 3ml of 0.2 M electrolyte solution, CuSO_4 , AlCl_3 and AgNO_3 , and heated it until 40°C. Then we added PEI (dissolved in hot water), after that stirring for 5 hours. Ultra sonication was used until homogeneous, and the complete dispersal of NPs inside polymers chains occurred.

2.2.3 Copolymers (PEI –g-PDMS) molding

A percent (50 v /50v) of PDMS/Graphene and composites was mixed in a PEI solution, then curing agent B was added in a weight ratio of 10:1 of total volume, The mixture was put under a vacuum oven at room temperature for 30 minutes to remove the bubbles completely, and then it was picked at 60 °C for four hours.

Afterward, from our understanding, Graphene nanomaterials have good electric properties because charged electrons move easily through carbon by forming resonance outside of the bonds (C=C) that transfer the electrical charge p high to permit electrical conductivity. Subsequently, adding or grafting a small number of carbon nanoparticles or Graphene alternatives to nonconductive polymers will improve the impact of their surface, increase surface area, and reduce resistivity. For that reason, polymer nanocomposites could be applied to biological sensors, electronic fabrication, or automotive and aerospace manufacturing. Extensive research on assembling or grafting different sorts of polymers by different composites ceramic or inorganic materials to improve the different characteristics of new composites (mechanicals, chemicals, and thermal) has been carried out. One factor should be considered: the preparation method and the process of creating the nanocomposite matrix, and physical properties like the aggregation and deposition or depletion of carbon sheets can affect its electrical performance. Nanofibers, graphene sheets, and nanotubes (SWNT or MWNT) produced by different methods, the adhesion technique, matrix alignment, the dispersion between the nanomaterial and polymer, even chemical modification and purification have a great impact on the electrical conductivity of nanocomposites.

The imaginary peak is a part of the electric modulus (M'') supply input on long-domain of dipole motion, which results from the imaginary part of the impedance spectrum (Z'') (imaginary for the copolymer under discussion). The copolymer PDMS-g-PEI behaves like an electrolyte solution of different specious with dipole sites. On the other hand, there are interfaces between the nanoparticle dipoles and pairing electron on N atoms in PEI, which results in circles of resonance inside graphene structure, as shown in Fig. 1.

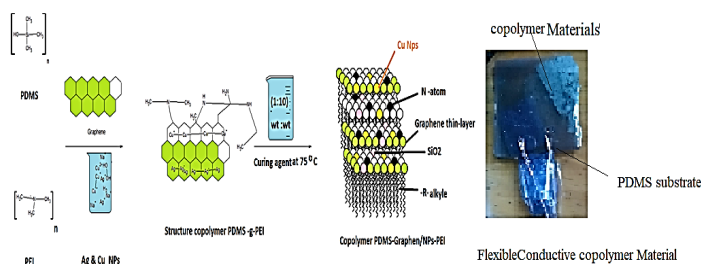


Fig. 1. Pathway of copolymer PDMS –Graphene /NPs- PEI preparation.

3. Results and discussion

3.1 Characterization

FTIR spectra were acquired using a Nicolet iS50 IR spectrometer association with KBr pellets. The PDMS morphology of graphene, PEI -NPs, and copolymer were investigated using a transmission electron microscope (JEM-2100F, Japan). The Current (I)–voltage (V) curves were measured by using an electrochemical working station (AUTO LAB PGSTAT100).

EIS characterization

The detection impedance of composite materials used for electrodes EIS analysis or electrochemical analysis was investigated using a Multidetector connected with a Frequency Analyzer (MPFA). Its potentiostat-galvanostat joint with eight channels is used for electrochemical characterization and electrolytes battery studies (10V, 4A). It is designed as Corrware/Corrview system to facilitate the implementation of all electrochemical methods associated with the 1255B frequency analyzer to detect or estimate OCV and CV. This is achieved by taking a thin layer or cylinder from different electrolyte polymers, then putting them in a sample shape (e.g., coin cell) sandwiched between two proper electrodes conducted through impedance at frequencies between 2MHz and 1.5 kHz at open cycle voltage (OCV = 0.39) using three electrodes, a working electrode (glassy), a reference Ag/Ag Cl electrode and a counter electrode.

Real impedance (Z') indicated the sample's ohmic resistance, while imaginary (Z'') calculates non-ohmic resistance. We can summarize the EIS characterization by some inhomogeneous changes regarding the polymer conductivity. The analysis mechanism is related to any development or change of double-layer electrode, and polymer surface is visible as a minimum of Z'' as a frequency function. A Nyquist plot curve applicable to electronic circuits is used to estimate the electrical or electrochemical parameters, especially on charge transfer and resistance in the system (See Fig. 2).

We noticed an inverse proportion of resistance conductivity by investigating the specific resistance of different prepared compounds (PDMS-g-PEI, electrolyte Ns, PDMS-graphene, and PEI-NPS), which depends on the free of movement of ionic charges inside the compound. In the case of the liquid electrolyte (0.2M of CuSO_4 and AgNO_3), we found a lower resistance (Z' value) compared to another flexible, stretchable polymer. We also recorded that the conductivity of PEI/NPS is higher than PDMS-graphene. It might be that the NPS (Ag, Cu) created new sites with an amines group (dual characterization). A pair of electrons charge the transfer, and an Ag-Ag and Cu-cu metallic bond losses an electron, and numerous electron charges feed the polymers. On the other hand, we found that the PDMS-graphene conductivity is increased by coupling or co blocking with PEI/NPS. Our explanation for those phenomena could be that free ions created by PEI/NPs cause a Graphene resonance (π - π) bond inside the grapheme structure (PDMS-graphene). Otherwise, due to nanoparticles (Ag and Copper) impregnated inside a matrix synthesis, different active sites are needed to improve charge or ions. Table 1 shows the calculation for the electric conductivity using the following expression,

$$R = \rho \frac{L}{A} \quad \text{and} \quad \sigma = \frac{1}{\rho} = \frac{L}{AR}, \quad (1)$$

where ρ indicates the material resistivity, L is the material's length, A is the polymer area, and L/A is the cell constant. Since R can be acquired by the EIS plot, we can detect the σ for prepared composites polymer. The conductivity of the electrolyte solution PDMS-b-PEI-PEI-NPs-PDMS-Graphene is shown below in Table 1.

Table 1. shows the conductivity measurements of prepared materials

Materials Composite	L/A (cm ⁻¹)	R _i A (Ω cm ²)	σ (S cm ⁻¹)
PDMS-b-PEI	3.3×10 ⁻²	6.09×10 ²	1.87×10 ⁻⁴
PDMS-Graphene	2.56×10 ⁻²	3.55×10 ³	1.04×10 ⁻⁵
PEI-NPs	1.4×10 ⁻²	4.55×10 ⁴	3.67×10 ⁻⁷
Electrolyte solution	-	-	5.64×10 ⁻⁶

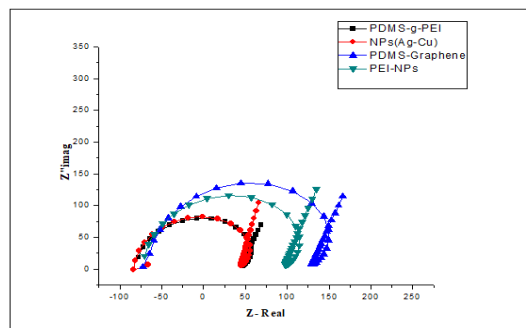


Fig. 2. The impedance of different prepared solutions used to copolymer composition.

Fourier transform infrared spectroscopy

FTIR analysis was carried out on 50 μ m thick PDMS-b-PEI, PEI-NPs, and PDMS-Graphene film, to investigate the effect of grafting and assembled of composites on the properties of functional groups of polymers. The FTIR characterization was done by an Equinox FTIR Spectrometer (Billerica, MA, Bruker Optics) provided a KBr beam splitter. Each prepared sample has been scanned at ambient temperature with a resolution of 4 cm^{-1} under inert nitrogen flux flow to eliminate any water vapor. The data were recorded in the wavelength around 4000–400 cm^{-1} using Bruker Optics OPUS (Bruker Optics) 4.0 software.

IR characterization

Fig. 3 shows a comparison between different composites of PDMS/graphene. In the FTIR spectra, we found two spectra at 845 and 1585 cm^{-1} for the carbon structure of carbon in graphene, which correspond to $\nu(\text{C}=\text{O})$ and corresponds to peak 1743 cm^{-1} at typical of carboxyl moieties. Another carboxyl group slightly appears around to 1346 cm^{-1} . A weak peak noticed at 1575 cm^{-1} , appoint to $-\text{C}=\text{C}$ in the spectrum might be resonance phenomena inside the graphene ring related to electron transfer or π - π bond interface interaction between graphene structure and SiO_3 of PDMS polymer at band 785 cm^{-1} and 915 spectra provides good evidence for $\nu(\text{Si-OH})$ and $\nu(\text{OH})$ respectable out of the plane. Also, at 1105 cm^{-1} is concerned with Si-O-Si and Si-O-C vibrations. There is a high-intensity absorbency at 1740 cm^{-1} , a spectrum corresponding to the $\nu(\text{C}=\text{O})$ group vibration, which is shifted by a combination of organic carbon chain graphene. The explanation for the spectrum of PDMS/graphene detection signals is that it is assigned at 1257 cm^{-1} and 1099 cm^{-1} inclusive Si-C stretching vibration. The other reason for forming the matrix polymer or composites matrix is that no spectra appear. Functionalized graphene is not found between 790 and 950 cm^{-1} , which means coordination of the bond related to Si-OH groups.

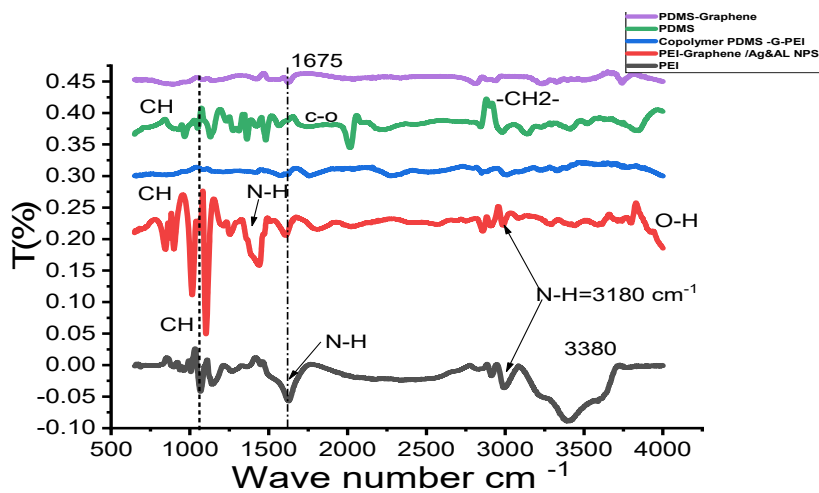


Fig. 3. IR spectrum characterization

Fig. 3 shows a comparison between different composites PDMS/graphene FTIR spectra. We found two spectra at 845 and 1585 cm^{-1} for the carbon structure of carbon in graphene, according to Kastnert (1994) and Saito (1998). These correspond to $\nu(\text{C}=\text{O})$ and a peak of 1743 cm^{-1} at typical carboxyl moieties. Another carboxyl group makes a slight appearance around to 1346 cm^{-1} . A weak peak was noticed at 1575 cm^{-1} , appoint to $-\text{C}=\text{C}$ in the spectrum. It might be resonance phenomena inside graphene ring related to electron transfer or π - π bond interface interaction between graphene structure and SiO_3 of PDMS polymer at band 785 cm^{-1} and 915 spectrum. This is great evidence that $\nu(\text{Si-OH})$ and $\nu(\text{OH})$ is respectable out of the plane. Also, at 1105 cm^{-1} is concerned for Si-O-Si and Si-O-C vibrations. High-intensity absorbents at 1740 cm^{-1} , a spectrum corresponding to $\nu(\text{C}=\text{O})$ group vibration, were shifted by a combination of organic carbon chain Graphene. The explanation for the spectrum of PDMS/graphene detection signals is assigned at 1257 cm^{-1} and 1099 cm^{-1} inclusive Si-C stretching vibration. The other reason for forming the matrix polymer or composites matrix is that no spectra appear. Functionalized graphene is not found around 790 and 950 cm^{-1} , which means coordination bonds related to Si-OH groups.

On the other hand, structural features of the copolymers were established by FT-IR spectroscopy. Fig. 3 displays the FT-IR spectra of the copolymers as an example. There is no obvious variance of intensity, and the band absorption positions are found between the block copolymers and are randomly segmented.

Raman Spectroscopy

We used Raman spectroscopy as another confirmation technique besides IR. It is a nondestructive technique that gives related structural information on carbon-skeleton materials or polymers. Raman spectroscopy of PDMS-graphene composite shown in Fig. 4 was carried out using a laser (wavelength 532 nm). The carbon group for the PDMS-peak wavelength spectrum

is situated between $1300\text{--}1400\text{ cm}^{-1}$ and peaks slightly around $1550\text{--}1615\text{ cm}^{-1}$ for characteristic peaks of graphene Nano powder (Kim et al., 2017). There is a proportional relationship between the intensity of graphene and PDMS polymer carbon structures, and we can demonstrated resonating charge formed on carbonyl group, lead to starched $\text{C}=\text{O}$ saturated $\pi\text{-}\pi$ bond to $n\text{-}\pi$ in excited state. The increasing intensity with more graphene inside the polymer matrix demonstrated the well-dispersed and uniform distribution of graphene in a PDMS polymer cross-section. Also, there are considerable and progressive changes of intensity and widening of PDMS characteristic peaks before and after mixing with Nano powder Graphene, confirmed with TEM analysis (as will be shown later in Figs. 7-9).

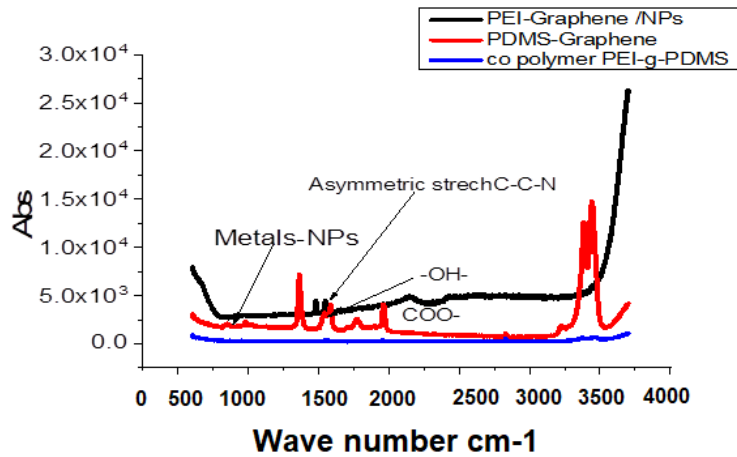


Fig. 4. Raman analysis for different composites.

Fig. 5 displays the spectrum intensity for nanoparticles (Ag and Cu) on the surface of PEI (polyethyleneimine) with spread speak appearing for PEI structure, especially for the (NH) amines group—confirming the assembly of nanoparticles on the PEI polymer. We also used UV spectrum analysis for a more detailed understanding.

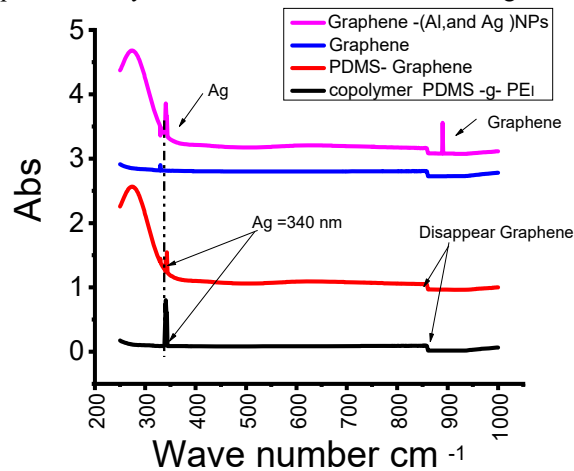


Fig. 5. UV for composite structures.

To be more accurate, we use another optical characteristic for the prepared composite polymer. UV spectroscopic has been conducted to measure both direct and diffused light. Fig. 7 shows that various spectrum absorbents at different wavelengths are a concept of Lambert's law. By comparing three spectra of absorbance PDMS/graphene, NPs/PEI, and copolymers, we found the absorbent properties change intensity. There is significant evidence that the nanoparticles Ag, Cu, Al (suspended in electrolyte solution), and Nano graphene filled the transmitted space (gaps), and the recorded height transmitted and disappears in other peaks in our structure. On the other hand, there is another opinion explained, a large amount of graphene doping will produce fluorescence quenching, and only at a certain dose can graphene contribute to the improvement of optical properties. Therefore, there is no explanation for the generation and disappearance of Ag and graphene spectra (Pan et al., 2021).

SEM Characteristics

Scanning electron microscopy (SEM) SURFACE morphology was conducted using field emission Scanning Electron Microscopy involving a Quanta TM 3D FEG (FEI Company, USA) apparatus. All SEM images were created by an Everhart Thornley Detector (ETD) designed at a voltage of $5\text{e}30\text{ kV}$.

A scanning electron microscope (SEM) has been used to characterize the morphological surface features' cross-section of each PDMS and PEI, SEM. Fig. 6 shows that both of the polymers' surfaces are smooth without any cracking or deformation compared to Figs. 6a and 6b, which shows many cracks on the surface of different composite polymers varnished with graphene nanotubes and numerous nanoparticle conductive metals. Fig. 6(b) displays a graphene/PDMS composite matrix with some deflection and bending deformation on the composite composition. It is a good indicator that the new composite will be extremely flexible and wearable due to the PDMS' nature and because it is well stamped with graphene in the PDMS form. In the original PDMS, the SEM images are tidy and unruffled (without gaps or empty filler). One advantage of PDMS is that it might be subject to an electrostatic charge or polarity between the SiO₂ group and different nanoparticles when arranged in different shapes, as shown in Fig. 6b.

On the other hand, when the same description is applied to the PEI polymer before grafting nanoparticles, SEM image in Fig. 6a shows that the SEM surface is smooth without any fractures or faults. Figs 6a and 6b also show the SEM micrographs of the cross-section typically look like the previously prepared composites recorded before the literature review. There is an uncommonly uniform dispersal of graphene in some parts of the figure. Overall, this confirms that there is good compatibility dispersion between the two phases of the mixture. Throughout SEM morphology characterize, we also noticed random distribution of Graphene as well Metals Nano particles helps to improve transfer electric charge on composite structure

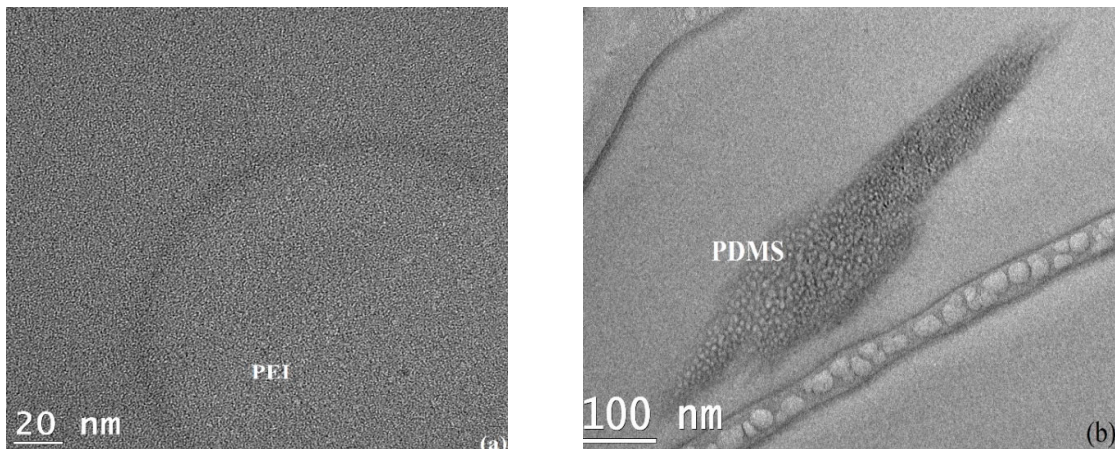


Fig. 6. SEM for a) PEI b) PDMS

TEM Characterization

All analyses were carried out by transmission Electron Microscope model H-9500 operated at 100-300 kV TEM accelerated electron gun Panorama LaB6, with a high diffraction pattern. Specimens were divided into single crystal silicon (Si) and quickened at a voltage range between 40Kv to 100Kv. A high-resolution camera with a diffraction length of 0.5m and a magnification between 18× and 450,000× was used with the resolution (objective lens) set to 0.5nm/5.0Å (point), 0.34nm/3.4Å (line).

Composite PDMS /Graphene

The images display excellent dispersal and the coalition of Nano Graphene in a long unfilled space of PDMS polymer. There is a big change between Figs. 7a and 7b, which confirms our explanation.

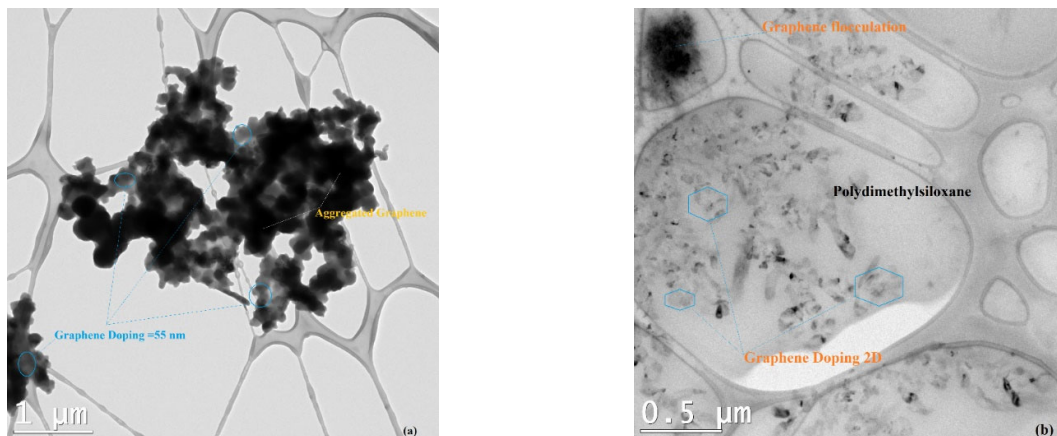


Fig. 7. TEM a) Graphene b) PDMS /Graphene solution

Furthermore, the change confirms that despite the existence of the PDMS component and good distribution of graphene inside the PDMS matrix, it will prevent agglomeration or sedimentation during the process, which leads to uneven physical properties of the composites. The TEM image indicates that the graphene nanostructure's walls are heterogeneous, rough, and spotted with extra materials compared to pure PDMS, as shown in Fig. 7a. We considered that some of the aggregation or deposition of graphene on the surface area of PDMS is rough in some parts and uniform in other parts of PDMS due to the preparation methods (density or concentration overview).

Graphene and (Ag, Cu) NPs assembled on PEI

Figs. 8a and 8b show that TEM contrast in PEI/NPs polymer is accomplished via silver particles assembled on the surface of PEI due to the Ag reflection energy atom. This makes it easier to create bonds between amines groups and silver atoms by gaining or losing electrons between two species. The size of Ag and Cu, around 10- 25 nm, causes filling in the PEI matrix cross-section. Furthermore, the homogeneity of PEI makes it easy to suspend fine nanoparticles in the solution. Also, Figure 8b indicates grafting nanoparticles (silver and copper) inside PEI polymer. It could be reforming new bonds between a pair of electrons on N-atoms and metal atoms of silver and copper particles through a metallic bond or galvanic bridge $Cu / Cu + // Ag - / Ag$. Regarding Fig. 8a we noticed Ag and Cu's distribution.

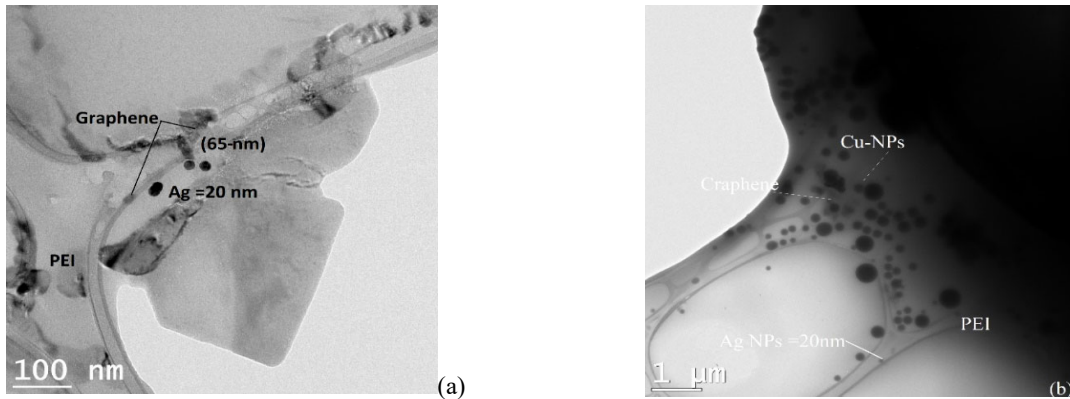


Fig. 8. TEM a) PEI –Graphene b) PEI-Graphene/NPs assembled.

Composites PDMS-g-PEI

TEM characterization is used to investigate and estimate the change of surface morphology of different prepared materials (Graphene-PDMS, PEI-NPs, and Copolymer PEI-g-PDMS). Figs. 9a and 9b illustrate the composition and dispersion of Nano-graphene in the filler space of PDMS compared to Fig. 6b, where it appears smooth without any flocculation or deposition. The surfaces show good dispersion of layered graphene into a homogeneous PDMS-urea copolymer solution of PDMS-g-PEI. A TEM image is shown in Figure 9a. NPs and graphene particles were recorded by distributed platelet shape with lower dimension than expected due to the formation of new composites inside polymers. Graphene-Cu or graphene-Ag composites or could be present because NPs spread on graphene surfaces, which prevents them from appearing in a large amount in Fig. 9b.

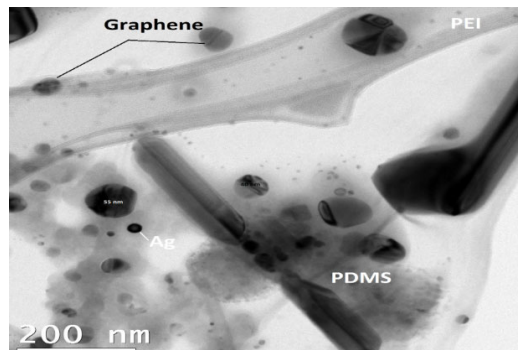


Fig. 9. TEM PDMS –Graphene /NPS –PEI Co-polymer composites.

Graphene Nanomaterials have good electric properties because charged electrons move easily through carbon by forming resonance outside of the bonds ($C=C$) that transfer the electrical charge p-hole to permit electrical conductivity. Furthermore, the TEM image in Figs. 9a and 9b explains both polymers' dispersal mechanism—integrated to form one copolymer without any distortion or voids. We believed the nanoparticles (Ag, Cu, and graphene) were chosen because each one has a unique physical and chemical property for forming chelating or bonded reactions together or with polymers carbon skeleton. Perfect

PDMS /composites matrices can be in effect processed via the solution preparation casting and curing. Fig. 9a and Fig. 9b show that the copolymer (PEI-g-PDMS) was formed with a highly diverse distribution of graphene, silver, and copper inside the matrix to form new composites copolymer, which is flexible, stretchable, and conductive.

Particle size analyzer

Zetasizer Nano S90 (Malvern) modal Nano S90 analyzer carried out a particle size analysis on the liquid phases. It is operated by Red laser (632.8nm, 4 mW) and used a Zetasizer instrument that works at a receptor angle equal to 90 degrees to make it easy to investigate and estimate particles suspended inside the liquid phase located between 1nm to 5 microns in diameter. Moreover, it is considered an important tool to evaluate and understand our colloidal solution and charge its physical properties, rheology behaviors, capacity, and efficiency ions charge, depletion, deposition, or precipitated particles. Figure 10 shows that the silver and copper nanoparticles are spread uniformly and suspended over the whole polyethyleneimine phase, which is good evidence of a new matrix's complete miscibility without any deformation. Furthermore, new sites or bonds will form. In addition, with the average volume of the particles at 193 nm, it is easier to carry a charge.

Fig. 10a shows that though the particle size is somewhat larger at 920 nm, it might be related to the electrostatic or inter-inter Vander Waals force between graphene depletion or its agglomeration a TEM of surface morphology confirmed it. This showed good dispersal in some areas and flocculated in PDMS-graphene. However, it could be caused by a chain of a double layer (ions charge) forming from outer layers of graphene walls, which makes tubes (resonance π - π bond). This will be the main reason for the augmentation of conductivity in the whole final composite copolymer.

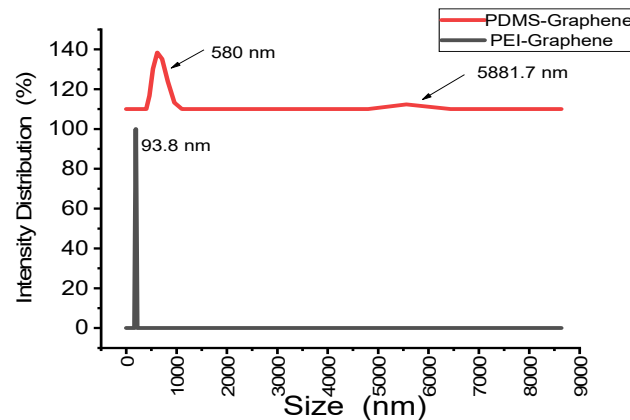


Fig.10. Particle size Analyzer a) PDMS /graphene b) PEI polymer assembled nanoparticles and graphene

An EDAX analysis was done for composite copolymer (PDMS-g-PEI) to illustrate the main composition of impregnated nanoparticles inside the copolymer skeleton structure. There are copper, silver, and carbon (Graphene), confirmed by previous analysis recorded in Figs. 11 and 12. The ion coupled plasma (ICP) for a sample of PEI-NPs contains the same elemental silver and copper composition, thus providing good evidence of the copolymer preparation (PDMS-g-PEI).

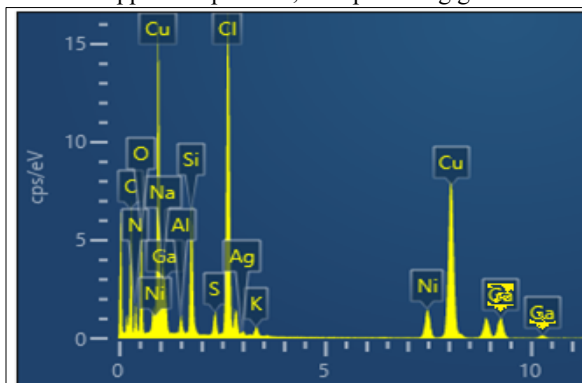


Fig. 11. EDAX characterization of copolymers

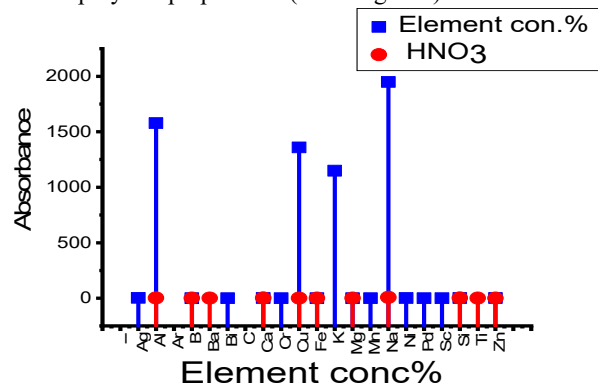


Fig. 12. ICP analysis PEI-NPs

3.2 Mechanicals characterization

The self-healing process and the tensile test are important methods to investigate our co-part polymers composites' mechanical properties. Fig. 13 shows large differences before and after a combination of copolymers (PEI-NPs and PDMS-graphene) form one block copolymer. In Fig. 12, two polymers are compared by increasing the tensile strain by 10% compared to the PDMS /graphene polymer. The results also expose that the self-healed composite copolymer's tensile strength regains up to 90% of its original value.

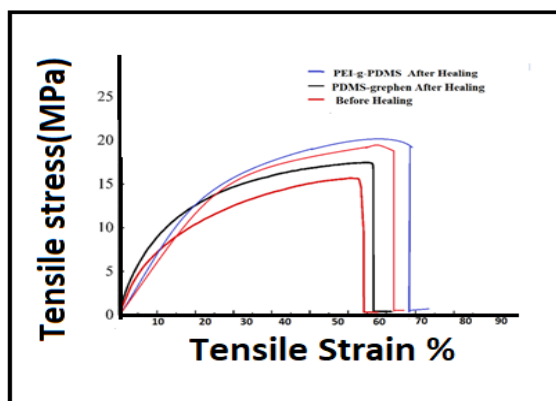


Fig. 13. Stress-strain of free-standing PDMS, and copolymers PDMS-graphene-PEI before and after the self-healing process

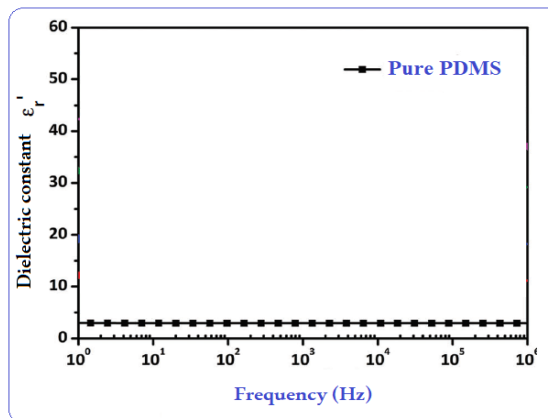


Fig. 14. Dielectric constant of PDMS substrate

3.3 Dielectric Substrate PDMS characterization

Dielectric phenomena is one specific characterize for PDMS substrate and should take in our consideration. Specifically, Dielectric properties PDMS substrate was deliberated using dielectric analyzer (Novocontrol BDS 20 GmbH),ETS Montreal. Samples were located in a vacuum chamber to avert errors during the measurements. By applying plasma treatment without any affect the dielectric response like other types of polymers reported in previous literature (Palmer et al., 2012). Fig. 14 points out the dielectric Properties pure PDMS .due to the polarization of function group Si-O-Si bonding, which appears as neutral, due to stability of a structure without external effect like bonding, interaction force or reacted with another active atom, that means PDMS without any treatment (grafting, assembling and block), which are responsible for enhancing of activity and conductivity of dielectric material. The measurement was based on the amount of the real and the imaginary value, which is relative to the relative permittivity of a pure structured PDMS material in a frequency range between 1 Hz to 10^6 Hz at ambient temperature. However, homogeneous nature of PDMS is one important case to give details of nonconductive that is equal to 2.69 as shown in Fig. 14.

4. Conclusion

To conclude, the copolymers' unique characteristics—robustness, flexibility, and good conductivity depend on the type of assembled nanomaterials, physical behaviors, and the chemicals created by bonding or chelating. The field of assembling or grafting carbon nanomaterials to diversify their properties creates applications in various fields. We created a flexible antenna that is easily applicable and non-toxic. We recorded the effect of grafting or combining nanoparticles graphene and copper and silver as a sandwich. We completely changed a new composite (copolymer) with nanostructures, such as graphene-carbon nanoform structures, by an sp^2 hybridization mechanism. Using organosilanes in addition to PEI (polyethyleneimine) to broaden carbon nanomaterial behaviors and properties is an important way should be overwork. The stretchable and formable patch antenna focuses on the material sandwich used in fabrication, such as PDMS-graphene/PEI-NPs composites. We have characterized, fabricated and investigated its improvement in all physical properties. For instance, we carried out electrochemical characteristics like EIS, impedance measurement to estimate new composites' conductivity, and comparison between initial and final product. In some of the mechanical tests applied to the copolymer structure, we noticed the new copolymer (PDMS-g-PEI) has healing and tension strain. Furthermore, numerous experiments and analyses have been conducting to prove the composite's composition, surface morphology, and nanoparticles distribution. In this way, we created a flexible, wearable electronic device that can be used in the future.

Acknowledgements

We would like to thank the former and current lab members of Prof. Mohmed sij and for his assistance and expertise in completing this research work in his laboratory in Nano-QAM , UQAM university, Montreal ,Canada

References

- Arnold, C. A., Summers, J. D., Chen, Y. P., Bott, R. H., Chen, D., & McGrath, J. E. (1989). Structure-property behaviour of soluble polyimide-polydimethylsiloxane segmented copolymers. *Polymer*, 30(6), 986-995.
- Baughman, R. H., Zakhidov, A. A., & De Heer, W. A. (2002). Carbon nanotubes--the route toward applications. *science*, 297(5582), 787-792.
- Biswas, A., Bayer, I. S., Biris, A. S., Wang, T., Dervishi, E., & Faupel, F. (2012). Advances in top-down and bottom-up surface nanofabrication: Techniques, applications & future prospects. *Advances in colloid and interface science*, 170(1-2), 2-27.
- Borah, D., Ozmen, M., Rasappa, S., Shaw, M. T., Holmes, J. D., & Morris, M. A. (2013). Molecularly functionalized silicon substrates for orientation control of the microphase separation of PS-b-PMMA and PS-b-PDMS block copolymer systems. *Langmuir*, 29(9), 2809-2820.

- Cai, L., Zhang, S., Miao, J., Yu, Z., & Wang, C. (2016). Fully printed stretchable thin-film transistors and integrated logic circuits. *Acs Nano*, *10*(12), 11459-11468.
- Chen, G., Pei, X., Liu, J., & Fang, X. (2013). Synthesis and properties of transparent polyimides derived from trans-and cis-1, 4-bis (3, 4-dicarboxyphenoxy) cyclohexane dianhydrides. *Journal of Polymer Research*, *20*(6), 1-11.
- Chen, M., Zhang, L., Duan, S., Jing, S., Jiang, H., & Li, C. (2014). Highly stretchable conductors integrated with a conductive carbon nanotube/graphene network and 3D porous poly (dimethylsiloxane). *Advanced Functional Materials*, *24*(47), 7548-7556.
- Coleman, J. N., Khan, U., Blau, W. J., & Gun'ko, Y. K. (2006). Small but strong: a review of the mechanical properties of carbon nanotube-polymer composites. *Carbon*, *44*(9), 1624-1652.
- Darling, S. B. (2007). Directing the self-assembly of block copolymers. *Progress in Polymer Science*, *32*(10), 1152-1204.
- Freebody, M. (Ed.). (2011). Preserving Moore's law pushes lithography to its limits. *Photonics Spectra*, *45*(5), 45-47.
- Fu, Y., & Manthiram, A. (2012). Enhanced cyclability of lithium-sulfur batteries by a polymer acid-doped polypyrrole mixed ionic-electronic conductor. *Chemistry of Materials*, *24*(15), 3081-3087.
- Gaynor, W., Burkhard, G. F., McGehee, M. D., & Peumans, P. (2011). Smooth nanowire/polymer composite transparent electrodes. *Advanced Materials*, *23*(26), 2905-2910.
- Ghoshal, T., Sentharamaikannan, R., Shaw, M. T., Holmes, J. D., & Morris, M. A. (2012). "In situ" hard mask materials: a new methodology for creation of vertical silicon nanopillar and nanowire arrays. *Nanoscale*, *4*(24), 7743-7750.
- Hamciuc, E., Hamciuc, C., & Cazacu, M. (2009). Comparative evaluation of some properties of two poly (ether-imide) thin films with/without fluorine in the structure. *Rev Roum Chim*, *54*, 1007-1013.
- Hamra, A. A. B., Lim, H. N., Hafiz, S. M., Kamaruzaman, S., Rashid, S. A., Yunus, R., ... & Huang, N. M. (2018). Performance stability of solid-state polypyrrole-reduced graphene oxide-modified carbon bundle fiber for supercapacitor application. *Electrochimica Acta*, *285*, 9-15.
- Hirai, T., Leolukman, M., Liu, C. C., Han, E., Kim, Y. J., Ishida, Y., ... & Gopalan, P. (2009). One-step direct-patterning template utilizing self-assembly of POSS-containing block copolymers. *Advanced Materials*, *21*(43), 4334-4338.
- Hwang, J., Jang, J., Hong, K., Kim, K. N., Han, J. H., Shin, K., & Park, C. E. (2011). Poly (3-hexylthiophene) wrapped carbon nanotube/poly (dimethylsiloxane) composites for use in finger-sensing piezoresistive pressure sensors. *Carbon*, *49*(1), 106-110.
- Jiao, J., Zhang, H., Yu, L., Wang, X., & Wang, R. (2012). Dispersion of carbon nanotubes with the aid of surface-active ionic liquids 1-dodecyl-3-methyl-pyrrolidinium bromide. *Journal of Molecular Liquids*, *171*, 6-10.
- Kazaoui, S., Minami, N., Nalini, B., Kim, Y., & Hara, K. (2005). Near-infrared photoconductive and photovoltaic devices using single-wall carbon nanotubes in conductive polymer films. *Journal of applied physics*, *98*(8), 084314.
- Kim, D., & Yun, K. S. (2013). Patterning of carbon nanotube films on PDMS using SU-8 microstructures. *Microsystem technologies*, *19*(5), 743-748.
- Kim, H. S., Waqued, S. C., Nodurft, D. T., Devarenne, T. P., Yakovlev, V. V., & Han, A. (2017). Raman spectroscopy compatible PDMS droplet microfluidic culture and analysis platform towards on-chip lipidomics. *Analyst*, *142*(7), 1054-1060.
- Kim, J. U., Lee, S., & Kim, T. I. (2016). Recent advances in unconventional lithography for challenging 3D hierarchical structures and their applications. *Journal of Nanomaterials*, *2016*.
- Kim, K. S., Zhao, Y., Jang, H., Lee, S. Y., Kim, J. M., Kim, K. S., ... & Hong, B. H. (2009). Large-scale pattern growth of graphene films for stretchable transparent electrodes. *nature*, *457*(7230), 706-710.
- Krea, M., Roizard, D., Moulai-Mostefa, N., & Sacco, D. (2004). New copolyimide membranes with high siloxane content designed to remove polar organics from water by pervaporation. *Journal of Membrane Science*, *241*(1), 55-64.
- Kurdi, J., & Tremblay, A. Y. (2003). Improvement in polyetherimide gas separation membranes through the incorporation of nanostructured metal complexes. *Polymer*, *44*(16), 4533-4540.
- Lee, J., Lee, P., Lee, H., Lee, D., Lee, S. S., & Ko, S. H. (2012). Very long Ag nanowire synthesis and its application in a highly transparent, conductive and flexible metal electrode touch panel. *Nanoscale*, *4*(20), 6408-6414.
- Lee, S. H., Lee, D. H., Lee, W. J., & Kim, S. O. (2011). Tailored assembly of carbon nanotubes and graphene. *Advanced Functional Materials*, *21*(8), 1338-1354.
- Li, H. W., & Huck, W. T. (2004). Ordered block-copolymer assembly using nanoimprint lithography. *Nano Letters*, *4*(9), 1633-1636.
- Li, J., Cheng, X., Sun, J., Brand, C., Shashurin, A., Reeves, M., & Keidar, M. (2014). based ultracapacitors with carbon nanotubes-graphene composites. *Journal of Applied Physics*, *115*(16), 164301.
- Liaw, W. C., Chang-Chien, J., Kang, H., Cheng, Y. L., & Li-Wen, F. U. (2008). A straightforward synthesis and characterization of a new poly (imide siloxane)-based thermoplastic elastomer. *Polymer journal*, *40*(2), 116-125.
- Liu, G. (2002). *Investigation of ductile fracture under tensile high rate loading* (Doctoral dissertation, Carleton University).
- Mack, C. A. (2011). Fifty years of Moore's law. *IEEE Transactions on semiconductor manufacturing*, *24*(2), 202-207..
- Mahoney, C. M., Gardella, J. A., & Rosenfeld, J. C. (2002). Surface characterization and adhesive properties of poly (imidesiloxane) copolymers containing multiple siloxane segment lengths. *Macromolecules*, *35*(13), 5256-5266..
- Mahoney, C. M., Gardella, J. A., & Rosenfeld, J. C. (2002). Surface characterization and adhesive properties of poly (imidesiloxane) copolymers containing multiple siloxane segment lengths. *Macromolecules*, *35*(13), 5256-5266.
- Mao, G., Saboungi, M. L., Price, D. L., Badyal, Y. S., & Fischer, H. E. (2001). Lithium environment in PEO-LiClO₄ polymer electrolyte. *EPL (Europhysics Letters)*, *54*(3), 347.
- Mata, A., Fleischman, A. J., & Roy, S. (2005). Characterization of polydimethylsiloxane (PDMS) properties for biomedical micro/nanosystems. *Biomedical microdevices*, *7*(4), 281-293.
- McGrath, J. E., Dunson, D. L., Mecham, S. J., & Hedrick, J. L. (1999). Synthesis and characterization of segmented polyimide-polyorganosiloxane copolymers. *Progress in Polyimide Chemistry I*, 61-105.

- Mirkhani, S. A., Arjmand, M., Sadeghi, S., Krause, B., Pötschke, P., & Sundararaj, U. (2017). Impact of synthesis temperature on morphology, rheology and electromagnetic interference shielding of CVD-grown carbon nanotube/polyvinylidene fluoride nanocomposites. *Synthetic Metals*, 230, 39-50.
- Noh, J. S. (2016). Conductive elastomers for stretchable electronics, sensors and energy harvesters. *Polymers*, 8(4), 123.
- Pötschke, P., Kobashi, K., Villmow, T., Andres, T., Paiva, M. C., & Covas, J. A. (2011). Liquid sensing properties of melt processed polypropylene/poly (ϵ -caprolactone) blends containing multiwalled carbon nanotubes. *Composites science and technology*, 71(12), 1451-1460.
- Palmer, M. V., Thacker, T. C., Waters, W., Gortázar, C., & Corner, L. A. (2012). *Veterinary medicine international*, 2012.
- Pan, Y., Wang, L., Su, X., Gao, D., & Cheng, P. (2021). Nanolasers Incorporating $\text{Co}_x\text{Ga}_{0.4-x}\text{ZnSe}_{0.4}$ Nanoparticle Arrays with Wavelength Tunability at Room Temperature. *ACS Applied Materials & Interfaces*, 13(5), 6975-6986.
- Raquez, J. M., Habibi, Y., Murariu, M., & Dubois, P. (2013). Polylactide (PLA)-based nanocomposites. *Progress in Polymer Science*, 38(10-11), 1504-1542.
- Ren, J., Zhou, J., & Deng, M. (2010). Morphology transition of asymmetric polyetherimide flat sheet membranes with different thickness by wet phase-inversion process. *Separation and purification technology*, 74(1), 119-129.
- Shin, M. K., Oh, J., Lima, M., Kozlov, M. E., Kim, S. J., & Baughman, R. H. (2010). Elastomeric conductive composites based on carbon nanotube forests. *Advanced materials*, 22(24), 2663-2667.
- Stankovich, S., Dikin, D. A., Dommett, G. H., Kohlhaas, K. M., Zimney, E. J., Stach, E. A., ... & Ruoff, R. S. (2006). Graphene-based composite materials. *nature*, 442(7100), 282-286.
- Vaglio Pret, A., Poliakov, P., Gronheid, R., Blomme, P., Miranda Corbalan, M., Dehaene, W., Verkest, D., Van Houdt, J. D. ..(2012) Microelectronic Engineering; Elsevier, Vol. 98, pp 24-2804.013.
- Wohl, C. J., Atkins, B. M., Belcher, M. A., & Connell, J. W. (2012). Synthesis, characterization, topographical modification, and surface properties of copoly (imide siloxane) s. *High Performance Polymers*, 24(1), 40-49.
- Woo, J. Y., Kim, K. K., Lee, J., Kim, J. T., & Han, C. S. (2014). Highly conductive and stretchable Ag nanowire/carbon nanotube hybrid conductors. *Nanotechnology*, 25(28), 285203.
- Xu, F., & Zhu, Y. (2012). Highly conductive and stretchable silver nanowire conductors. *Advanced materials*, 24(37), 5117-5122.
- Yadav, S. K., Kim, I. J., Kim, H. J., Kim, J., Hong, S. M., & Koo, C. M. (2013). PDMS/MWCNT nanocomposite actuators using silicone functionalized multiwalled carbon nanotubes via nitrene chemistry. *Journal of Materials Chemistry C*, 1(35), 5463-5470.
- Yakuphanoglu, F., & Şenkal, B. F. (2007). Electronic and thermoelectric properties of polyaniline organic semiconductor and electrical characterization of Al/PANI MIS diode. *The Journal of Physical Chemistry C*, 111(4), 1840-1846.
- Yan, C., Wang, J., Kang, W., Cui, M., Wang, X., Foo, C. Y., ... & Lee, P. S. (2014). Highly stretchable piezoresistive graphene-nanocellulose nanopaper for strain sensors. *Advanced materials*, 26(13), 2022-2027.
- Yilgör, İ., & McGrath, J. E. (1988). Polysiloxane containing copolymers: a survey of recent developments. *Polysiloxane copolymers/anionic polymerization*, 1-86.
- Yu, M., He, Q., Yu, D., Zhang, X., Ji, A., Zhang, H., ... & Dai, Z. (2012). Efficient active actuation to imitate locomotion of gecko's toes using an ionic polymer-metal composite actuator enhanced by carbon nanotubes. *Applied Physics Letters*, 101(16), 163701.
- Zhang, S., Li, Y., Tian, Q., Liu, L., Yao, W., Chi, C., ... & Wu, W. (2018). Highly conductive, flexible and stretchable conductors based on fractal silver nanostructures. *Journal of Materials Chemistry C*, 6(15), 3999-4006.



© 2022 by the authors; licensee Growing Science, Canada. This is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC-BY) license (<http://creativecommons.org/licenses/by/4.0/>).